

# 3


## Extrusion Overview

The extruder is the heart of all extrusion processes, continuously heating and mixing the feed material as it supplies a homogeneous melt to the die for shaping. Although the emphasis of this book is on the hardware and methods specific to blown film extrusion, this chapter provides a general overview of the extruder and its functions. Final product quality and production efficiency are highly dependent on the operation of the extruder.

This chapter covers two main sections: extruder hardware systems and extrusion functional zones. The first section identifies the primary components of the extruder and provides detail regarding their capabilities and size ranges. The second section describes how the hardware interacts with the material as it passes through the system. In other words, it provides a look at what is happening inside each zone of the extruder. The descriptions here are purposefully brief, serving as a foundation to support later discussions specific to blown film extrusion. If the reader is interested in pursuing this topic further, there are many books devoted entirely to the extruder and extrusion processes. For example, *Polymer Extrusion* by Rauwendaal [15] provides an excellent in-depth analysis. Other references are listed in the final section of this book [16–19].

### ■ 3.1 Extruder Hardware Systems

The purpose of the extruder is to feed a die with a homogeneous material stream at constant temperature and pressure. This definition highlights three primary responsibilities that the extruder must accomplish while delivering material to a shaping die. First, it must homogenize, or satisfactorily mix, the material. Second, the material entering the die must have minimal temperature variation with respect to both time and position within the melt stream. Third, there must be minimal melt pressure variation with time. It is important that the design and operation of an extrusion system consider all three of these objectives to produce a quality product.

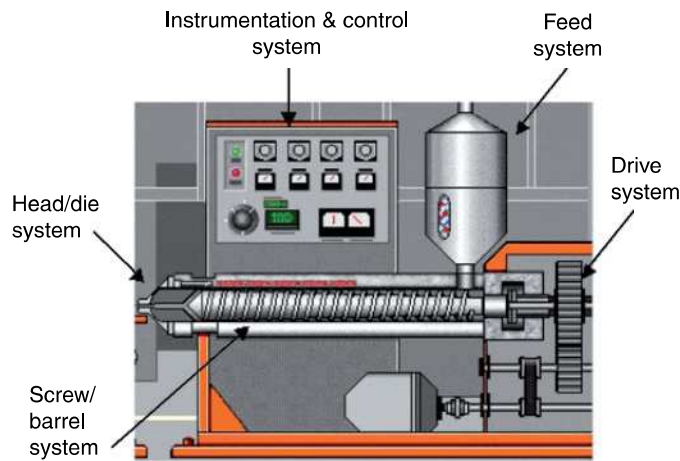

**Figure 3.1** The five extruder hardware systems

Extruders are generally rated by screw diameter. Typical production extruders range in size from 2 to 6 in (50 to 150 mm). A fundamental quantity determined by screw diameter is the maximum throughput measured in pounds/hour or kilograms/hour. The relationship between throughput and screw diameter is cubic, dependent upon the volume inside the extruder available for the polymer. With a certain polymer, a 2-inch extruder may have a maximum throughput of 100 lb/h, while a 4-inch extruder would have a maximum throughput of 800 lb/h. Therefore, system requirements such as material handling capacity, motor size, cooling capability, and floor space increase rapidly with an increase in screw size.

Components of the extruder hardware can be categorized into five systems (Figure 3.1):

- Drive system
- Feed system
- Screw/barrel system
- Head/die system
- Instrumentation and control system



**Simulator Exercise:** When the cursor is paused over any extruder component, an identification tag shows the name of that component.

### 3.1.1 Drive System

The drive system supplies the mechanical energy to the polymeric material by rotating the screw. This system consists of a motor, a speed reducer, and a thrust bearing.

#### 3.1.1.1 Motor

The motor is the source of power to turn the screw. Extruder motors tend to be relatively large due to the high power consumption by the polymer around the screw. Three sources of power consumption are 1) melting of solids via frictional heat generation, 2) conveying of high-viscosity molten polymer along the barrel, and 3) pumping of high-viscosity molten polymer through the die restriction. A rule of thumb for motor size is:

$$\text{Motor power (hp)} \cong \text{Throughput (lb/h)} \div 5$$

Extruder motors are usually electric, but some systems utilize hydraulic motors. For example, on injection and blow molding machines that use hydraulics to develop clamp tonnage, the extruder is also generally hydraulic. Electric motors are designed for either direct current (DC) or alternating current (AC). Traditionally, DC motors, which regulate speed through voltage control, have been more popular because they could provide the necessary power at a lower cost. However, recent advances in frequency control – the technique used to regulate speed in AC motors – have caused this type of motor to become more widely used.

#### 3.1.1.2 Speed Reducer

Electric motors generally operate most efficiently at high rotational speeds. A typical maximum speed for an extruder motor is 2,000 rpm. However, extruders for blown film are usually designed to operate at much lower screw speeds. Therefore, the high motor speed is geared down to a lower screw speed with the help of a *speed reducer*, also known as a *gear box*.


Gear boxes usually have reduction ratios in the range of 10 : 1 to 20 : 1, resulting in typical maximum screw speeds of 100 to 200 rpm. Besides speed reduction, the gear box provides an additional advantage of increased torque. This would be analogous to providing rotational leverage. Because of the high power consumption of polymeric materials, high torque is needed to maintain screw speed. Most drive systems are designed to keep screw speed constant even if the torque requirement changes, which could be created, for instance, by a change in material viscosity.



**Figure 4.20** A dual-station turret winder (*Windmoeller & Hoelscher*)

## ■ 4.11 Film Treatment

Polyolefins, such as polyethylene and polypropylene, are non-polar polymers. This means that any polar materials will not easily wet the surface of (adhere to) these polymers. One area where this has important implications is in the printing conversion process. Inks cannot be absorbed into most films because they are typically nonporous. The only way the ink will stay on the surface of the film is if it wets the polymer rather than puddle up. To promote the ink adhering to the surface, it becomes necessary to treat the film to make it more polar.

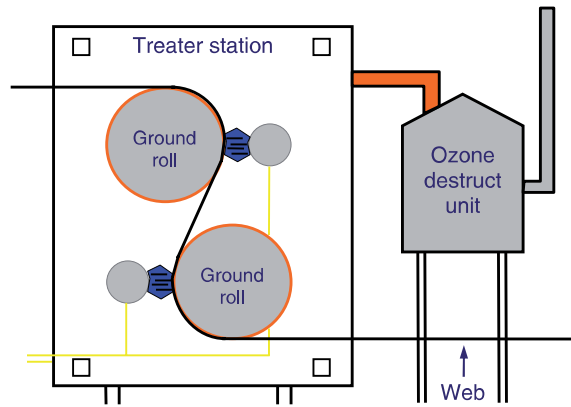

**Figure 4.21** Corona discharge unit for treating (oxidizing) film surfaces (*Pillar Technologies*)

The most popular treatment process for blown film is the corona discharge method. Corona discharge units (Figure 4.21) are high-voltage devices that ionize the air in a small region through which the film travels. The ionization creates ozone, a very strong oxidizing chemical. The result is that the film is oxidized, creating a polar surface rich with oxygen atoms [32]. The level of oxidation needed for a given film may depend to some extent on the additive package in the raw material. Also, this type of surface treatment is not permanent. In most cases, the film must be printed within a few days of treatment because additives in the plastic may migrate (bloom) to the surface and inhibit the treatment.

Safety is a top concern where these high-voltage corona discharge systems are employed. Adequate venting is necessary in the vicinity of the corona to extract the ozone created by the discharge unit. Also, a shut-off interlock should be used in the event of a film line break.

## ■ 4.12 Line Control

The goal of line control is to maintain minimum variation in all measurable film quantities with respect to both position and time. In other words, minimal variation is desired in a measurement such as film thickness from one position on the bubble to another and, at a given position, from one time to another. The high interdependence of process variables on film quality makes this an ambitious objective.

Sophisticated control systems have been developed in response to the high interdependence of several process variables coupled with the demands of very high output rates [33]. While many lines still utilize primarily manual controls, a majority

of blown film systems depend on computer-based measurement and control of all key process variables. These computer-based systems can make an important contribution to increasing efficiency, reducing costs, and increasing profits on high-output lines.

This section explains how film dimensional and property consistency results from maintaining process uniformity in four key areas:

- Melt from the extruder (or melt quality)
- Film thickness (or gauge)
- Layflat width (or, alternatively, bubble diameter)
- Frost line height

The following paragraphs focus on achieving uniformity in each of these four areas.

Providing high melt quality to the die is the primary objective of the extruder. High melt quality can be defined as homogenous material of constant temperature and pressure. Homogeneity of the melt depends on several factors, such as the uniformity of the raw material, adequate melting capability of the screw, and adequate mixing capability of the screw and/or static mixer. Raw materials are often sampled in-house or at an outside testing facility to ensure minimal lot-to-lot variation. Variations in the composition ratio of solids (the ratio of first-generation, reprocessed, fluff material, and additives) entering the extruder can lead to non-uniformities in the melt, and therefore should be minimized as an objective of the feed system. Finally, screw design is the critical element in ensuring that stable melting of solids occurs along the barrel and that the melt leaves the extruder adequately mixed.


To maintain a constant melt temperature, we must consider potential variations with respect to both position and time. Position variations refer to temperature differences between, for example, the wall surface of a melt stream and the internal core. If melt with a large temperature distribution enters the die, it can result in different temperature streams flowing to different positions around the die exit. This leads to gauge variations. Methods to reduce these variations include screw mixing elements, static mixers after the extruder, and flow channel design within the die. Time-dependent temperature variations (large swings from high to low) must be minimized by the extruder temperature control system. Additionally, screw speed stability and feed material consistency are crucial for good temperature control.

Constant melt pressure is the final requirement for high melt quality. The pressure of the melt entering the die, or head pressure, is determined by three variables: head/die flow channel geometry, polymer flow rate, and polymer viscosity. In general, the hardware geometry remains fixed, therefore pressure fluctuations are caused by any changes in flow rate or viscosity as described in the next two paragraphs. However, one change related to hardware geometry, or more specifically

flow restriction, is the buildup in front of filtering screens. Monitoring this buildup of contamination is important because of its effects on increasing head pressure, which impacts safety and process efficiency.

Polymer flow rate is kept constant as long as the screw processes are stable. That is, the stability of solids conveying, melting, mixing, and melt pumping is necessary to maintain a uniform flow rate through the die. It is not uncommon, particularly with significant amounts of reprocessed feed material, for solid conveying characteristics to change throughout a run, leading to detrimental pressure fluctuations.

Polymer viscosity variations may be caused by changes in either the raw material or the feed composition. Additionally, we can see viscosity changes when there are variations in hardware temperature, such as may occur with an unstable temperature control circuit.

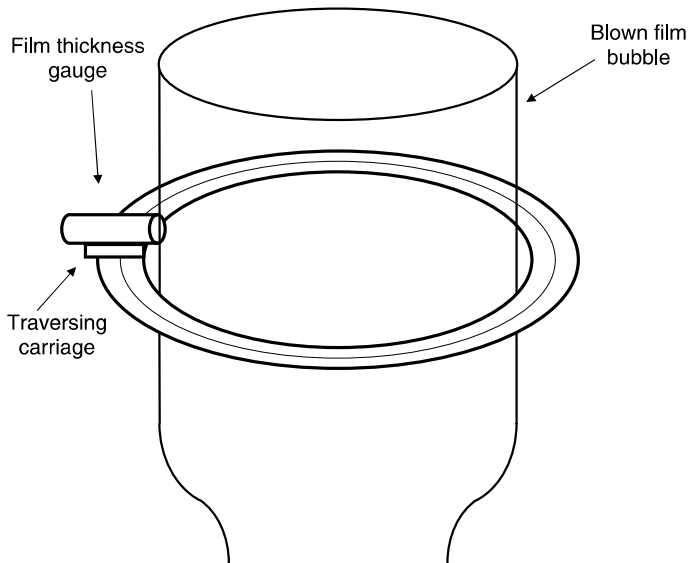

**Figure 4.22** A thickness gauge mounted on a carriage to rotate it around the bubble

The next process variable to be controlled is film thickness (gauge). Either on-line or off-line measurements allow us to monitor film gauge. On-line devices usually employ a radiation source, such as a gamma backscatter system. These devices measure thickness by emitting radiation that reflects back to the sensor from both the near and far surfaces of the film. They can be mounted to measure a fixed location on the bubble or on a carriage to traverse around the bubble (Figure 4.22). Also, a unit traversing back and forth across the flattened web can be used, but this measures two-layer thickness. One measurement unit uses software to separate the contributions from each layer in combination with an infrared sensor that is capable of distinguishing between the individual thicknesses in multilayer film

## ■ 5.1 Process Variables vs. Bubble Geometry

Table 5.1 defines the response that increasing either of the four main process variables (nip speed, screw speed, cooling speed, and bubble volume) has on each of the three main bubble geometric variables (film thickness, bubble diameter, and frost line height). An asterisk identifies the primary response to each increase.

**Table 5.1** The Effect of Each Main Process Variable on Bubble Geometry

Variable to increase	Film thickness	Bubble diameter	Frost line height
Nip speed	↓ *	↑	↑
Screw speed	↑ *	↑	↑
Cooling speed	↑	↓	↓ *
Bubble volume	↓	↑ *	↓

\* Primary response

This table highlights how making one adjustment in the process affects all three of the bubble characteristics. A skilled operator must understand these interrelationships to accurately adjust the process so that all the geometry requirements are within specification. Even though many blown film lines today are automated to adjust for changes in process conditions, the above relationships still exist and it is the responsibility of the system (manual or automatic) to take the proper corrective action.



**Simulator Exercise:** Try increasing each of the four variables in the table individually. During each increase, observe the effect on each quantity in the measurements panel. It may be beneficial to record and plot, using spreadsheet software such as Excel, the values with each change to see which measurements are affected most by each adjustment.

In the following paragraphs, a description is given of each of the relationships identified in Table 5.1. The assumptions here are:

1. only one process variable increases at a time while the others remain constant and
2. each response occurs naturally without correction from a closed-loop control (automatic measurement and adjustment) system.

When the nip speed increases, the primary effect is for the melt to be stretched more in MD, making the film thinner. As a result of the film traveling past the cooling air more quickly, the height on the bubble where the temperature has



dropped to the point of polymer solidification (the frost line) increases. (It is easy to mistakenly think that the frost line height should decrease because thinner film must cool faster. However, this is not the case because the effect of an increase in film speed is more significant and the frost line height always increases.) As the frost line height increases, the small diameter stalk below the frost line lengthens and the air volume in the bubble is displaced more to the top, because the bubble contains a fixed volume of air. This increase in bubble volume above the frost line pushes the bubble outward to a higher diameter, also contributing to film thinning.

An increase in screw speed results in an increase to all three bubble geometry variables. The increase in output from the extruder has the primary effect of increasing film thickness. Also, a greater amount of material results in a greater amount of heat that must be removed from the film. This takes a longer time under constant cooling conditions, thus increasing the frost line height. Again, as the frost line moves upward, the bubble diameter increases. The slight thinning effect due to an increase in bubble diameter is far outweighed by the thickness increase created by greater output.

Increasing the cooling air speed causes faster heat removal from the bubble. Because the film reaches solidification temperature sooner, the primary effect is a lowering of the frost line. As a result, the bubble diameter decreases from the constant internal air volume being distributed over a greater distance from frost line to nip rollers. Because a lower bubble diameter means the film is not stretched as much in TD, the film thickness increases.

When more air is inserted into the bubble, the bubble volume increases; primarily the diameter increases by stretching more in TD. The increased TD stretching results in thinner film. Thinner film cools more quickly, consequently lowering the frost line height.

## ■ 5.2 Characteristic Bubble Ratios

To properly describe and control the bubble-forming process, certain quantities have been developed to characterize the process conditions that influence bubble geometry. These quantities are the take-up ratio (TUR), the blow-up ratio (BUR), and the forming ratio (FR).

The TUR is the ratio of film velocity ( $V_f$ ) to melt velocity ( $V_m$ ), i. e.,  $TUR = V_f / V_m$ . This quantity provides an indication of the amount of stretching, hence molecular orientation, in MD. The film velocity is the upward speed of the film above the frost line and is established by the control system. It is equivalent to the nip speed. The

melt velocity is the upward speed of the molten polymer as it exits from the die lips. It is related to, but is not equal to, the screw speed. The melt velocity can be determined experimentally by marking the film and tracking the mark, but an easier method is to employ the principle of conservation of mass.

The conservation of mass states that the mass flow rate (pounds/hour) is equal at all points along the bubble. Mathematically,

$$m_{\text{rate}} = (\rho A V)_{\text{nip rollers}} = (\rho A V)_{\text{die gap}} \quad (5.1)$$

where  $\rho$  = density,  $A$  = annular area,  $V$  = velocity.


This equation can be rearranged to the form

$$\text{TUR} = V_f / V_m = (\rho A)_{\text{die gap}} / (\rho A)_{\text{nip rollers}} \quad (5.2)$$

The area of an annulus (Figure 5.1) can be calculated from the following equation:

$$A_{\text{annulus}} = \pi (R_o^2 - R_i^2) \quad (5.3)$$

where  $R_o$  is the outside radius and  $R_i$  is the inside radius of the annulus.



**Figure 5.1** Area of an annulus:  $A_{\text{annulus}} = \pi (R_o^2 - R_i^2)$

Since the nip speed is always greater than the melt speed, the TUR is always greater than one.

The BUR is the ratio of bubble diameter ( $D_b$ ) to die diameter ( $D_d$ ), i. e.,  $\text{BUR} = D_b / D_d$ . This quantity provides an indication of the amount of stretching, hence orientation, in TD. The bubble diameter is established by the control system and can be either measured directly or calculated by measuring the layflat (LF) width directly ( $D_b = 2 \text{ LF} / \pi$ ). The die diameter is fixed.

# Index

## A

additive 1, 11, 12, 13, 14, 15, 68, 70, 94, 95, 114, 122, 147, 148, 149  
air ring 5, 84, 86, 97, 98, 142, 143, 145  
ammeter 53  
amorphous 3, 5, 7, 9, 148  
antiblock additive 126  
antiblocking agent 12  
antioxidant 12, 70, 147  
antistat 12, 148

## B

bag VII, 1  
balloon VII  
barrel 38, 40, 41, 42, 44, 50, 51, 52, 53, 56, 57, 59, 63, 64, 72, 73  
barrier 9, 10, 15, 112, 113, 115, 116, 137  
– flight 147  
– property 110  
– type screw 75  
blocking 2, 12, 115, 126  
blower 84, 86, 98, 142, 143, 148  
blow-up ratio (BUR) 79, 103, 104, 107, 108, 109, 122, 143, 148, 161, 167  
branch 4, 5  
branched polymer 3  
branching 6, 28  
breaker plate 43, 44, 46, 52, 59, 136  
breathable 8, 115  
bridging 39, 55, 72  
brittleness 127

bubble diameter 82, 92, 98, 103, 104, 141, 143, 164  
bubble geometry VIII, 80  
bubble instability 142, 143  
bubble stability 29  
bubble volume 102, 103  
bulk density 13, 41, 55, 56, 71  
BUR 103, 104, 107, 108, 109, 148

## C

calcium carbonate 14, 62  
capillary rheometer 23  
capillary rheometry 130, 132  
carbon 15, 16  
clarity VIII, 1, 7, 9, 10, 11, 108, 110, 114, 115, 116, 128, 149  
clay 15  
clearance 41, 60, 76, 138, 140  
coefficient of friction 126  
coextrusion 8, 9, 10, 75, 76, 78, 88, 111, 112, 113, 114, 115, 149  
collapsing frame 90, 91, 150  
color 62  
colorant 13  
compression ratio 40, 58, 73, 74, 137  
consistency index 24, 134  
cooling 49, 51, 72, 73, 82, 83, 85, 88, 98, 102, 109, 128, 129, 137, 139, 142, 143, 145, 148, 149, 154  
corona discharge 94  
cost 1, 7, 11, 14, 15, 35, 64, 69, 75, 76, 85, 95, 101, 112, 115, 119, 131, 133, 137

crystalline 2, 123  
crystalline structure VIII  
crystallinity 2, 4, 5, 6, 7, 82, 88, 107, 116,  
128, 148, 149  
crystallization 28

## D

degassing 41, 54, 64  
degradation 10, 12, 16, 47, 60, 62, 70, 73,  
74, 110, 112, 122, 148, 149  
degraded 127, 137, 146  
density 2, 129, 164  
devolatilization 54, 64  
die 43, 44, 45, 47, 51, 52, 59, 63, 64, 65,  
75, 76, 78, 81, 86, 95, 97, 111, 112, 113, 114,  
132, 136, 141, 144, 147  
– design 30, 66, 67, 82, 112, 146, 149  
– diameter 4, 79, 81, 104, 148  
– drool 14, 65, 67, 68  
– forming 54, 65  
– gap 74, 75, 76, 79, 81, 82, 97, 105, 141,  
144, 146, 148, 164  
– line 146, 149  
– swell 65, 66  
dispersive mixing 61, 62, 63  
distributive mixing 61, 62, 63  
double bubble 10, 109  
downgauging 5, 10  
drag flow 20  
draw down ratio (DDR) 105, 168

## E

elastic behavior 19  
elongation 20, 123  
elongational rate 21  
elongational stress 21  
elongational thickening 28  
elongational viscosity 25, 30  
energy 42, 53, 57, 61, 62, 73, 74, 125,  
137, 138, 139, 147  
entanglements 25  
ethylene vinyl acetate (EVA) 8  
ethylene vinyl alcohol (EVOH) 9, 117

## F

feed throat 13, 38, 39, 41, 55, 72, 73  
filler 14, 15, 16  
film thickness VIII  
filter 8, 43, 44, 45, 46, 47, 138  
fisheye 127, 146  
flight 40, 41, 59, 60, 73, 75, 136, 138  
– clearance 58  
flood fed 39, 55  
fluff 54, 55, 70, 71, 95  
– regrind 38  
forming ratio (FR) 103, 105, 107, 108, 126,  
161, 167  
frost line height VIII, IX, 4, 81, 85, 92,  
98, 102, 103, 123, 142, 143, 148

## G

gauge 76, 95, 96, 97, 98, 113  
gear box 35, 36, 37, 42, 72  
gel 11, 12, 45, 73, 108, 127, 146  
glass 15  
gloss 128, 146  
grooved feed throat 4, 5, 39, 56, 59, 72,  
73, 74, 136, 138, 147

## H

haze 128  
head pressure 1  
heater band 51, 57, 58, 139  
heat-seal 1, 3  
high density polyethylene (HDPE) 4, 5,  
79, 83, 86, 115, 116, 129  
high stalk 86  
hopper 38, 39, 48, 53, 54, 55, 71, 72

## I

impact resistance 125, 126, 147, 148  
impact strength 101  
impact toughness VIII  
instrumentation 47  
insulation 47, 85, 86  
interfacial instability 114, 149

internal bubble cooling (IBC) 6, 98, 143  
 internal bubble pressure 82  
 internal bubble volume VIII, 82, 98

## L

layflat (LF) 104  
 – width IX, 82, 92, 98, 101, 148, 164  
 L/D ratio 41  
 linear low density polyethylene  
 (LLDPE) 5, 79, 82  
 line control 94  
 long stalk 4  
 – bubble 83  
 low density polyethylene (LDPE) 3, 4, 5,  
 7, 116, 129, 147  
 lubricant 14, 67, 68, 141

## M

masterbatch 11, 15  
 melt flow rate 26, 130, 131  
 melt fracture 1, 14, 65, 67, 114, 141, 149  
 melt index 116, 133  
 melting 53, 56, 57, 59, 75, 95, 136, 137,  
 138, 143  
 melt pumping 54, 59, 96  
 melt quality 42, 75, 76, 95  
 melt strength 1, 3, 4, 5, 7, 9, 11, 29, 31,  
 74, 75, 83  
 metallocene 7  
 metallocene polyethylene (mPE) 6, 116  
 mixing 41, 45, 54, 55, 60, 64, 74, 75, 95,  
 129  
 – element 63, 95  
 modified atmosphere packaging  
 (MAP) 115  
 molecular structure 24  
 molecular weight 25  
 molecular weight distribution 26  
 monolayer 2, 75, 116, 117  
 motor 34, 35, 36, 136, 154  
 – current 48, 53  
 mPE 116

multilayer 2, 8, 9, 10, 75, 115  
 – coextruded 7

## N

nip roll 82, 84, 90, 91, 92, 103, 126, 146  
 nip speed VIII, IX, 82, 92, 102, 103, 104,  
 148  
 nylon 110, 117, 147

## O

operator VIII, 97, 102, 131, 133, 138, 139,  
 141, 148, 151  
 orange peel 141  
 orientation VIII, 4, 5, 10, 22, 65, 101, 103,  
 104, 107, 108, 109, 122, 123, 124, 126, 148,  
 161

## P

packaging VII, 1, 8, 9, 10, 109, 110, 112,  
 115, 116  
 pellet 38, 53, 54, 55, 56, 70, 71, 73, 74,  
 146  
 PID control 49  
 pocket bubble 3, 82, 86  
 polyamide (PA) 10  
 polyethylene (PE) VII, 1, 2, 5, 7, 8, 9, 10,  
 14, 73, 74, 79, 83, 93, 115, 117, 123, 125,  
 127, 129, 136  
 polyisobutylene (PIB) 16, 17  
 polymer 1, 2, 4, 6, 7, 11, 12, 13, 14, 16, 41,  
 50, 52, 66, 74, 76, 82, 83, 93, 101, 112,  
 115, 117, 119, 122, 129, 132, 138, 147  
 polymer chemistry VIII  
 polymer processing aid (PPA) 14  
 polypropylene (PP) 6, 7, 31, 82, 93, 110  
 polystyrene (PS) 3, 7  
 polyurethane (PU) 11  
 polyvinyl chloride (PVC) 9, 16  
 polyvinylidene chloride (PVDC) 10, 110  
 powder 38, 39, 54, 70  
 power 3, 4, 14, 35, 49, 51, 57, 62, 64

power law index 24  
 PPA 14  
 pressure 33, 36, 37, 40, 41, 42, 43, 45,  
 46, 47, 48, 51, 52, 58, 59, 63, 64, 65, 67,  
 71, 73, 74, 78, 95, 112, 134, 136, 138, 139,  
 140, 149, 154  
 – flow 20  
 property VIII, 1, 6, 8, 9, 11, 12, 14, 15, 16,  
 67, 69, 70, 73, 82, 101, 105, 107, 108, 112,  
 113, 115, 117, 119, 120, 147, 149

## R

regrind 55, 136, 137  
 reinforcement 14, 15, 148  
 residence time 59, 78, 112, 137, 138, 147,  
 149  
 rheology 19  
 rupture disc 42, 51

## S

safety 51, 94, 96, 97  
 scratching 90  
 screen 59, 96, 140  
 – changer 45, 47, 138  
 – pack 44, 45, 138  
 screw 34, 35, 36, 37, 39, 40, 41, 44, 51,  
 53, 54, 56, 57, 59, 62, 63, 64, 65, 72,  
 73, 74, 132, 139, 147  
 – beat 136  
 – design 30, 58, 63, 74, 75, 95, 137, 138,  
 139, 149  
 – speed VIII, 7, 82, 95, 98, 102, 103, 104,  
 122, 134, 137, 138, 139, 141, 143, 148, 154  
 sharkskin 141  
 shear 20  
 shear rate 21, 132, 140, 141, 154  
 – effect on viscosity 23  
 shear stress 21  
 shear thinning 7, 24  
 shear viscosity 22  
 shelf life 115, 116  
 shrinkage 107, 109  
 shrink film 109, 116  
 simulator X, 151, 159

solid bed 57, 72, 140  
 solid bed breakup 53, 137  
 solid conveying 53, 54, 96, 136  
 specific heat 2, 83  
 speed reducer 35, 36  
 spider leg 76  
 spiral mandrel 75, 76, 77  
 stabilization 89  
 stabilizer 16  
 starve fed 39  
 static mixer 60, 63, 95  
 strain 19  
 stress 19  
 stretch hardening 28  
 surging 58, 73, 136, 137, 141, 143

## T

tackifier 16  
 take-up ratio (TUR) 103, 104, 107, 108,  
 109, 122, 141, 143, 148, 161, 166  
 talc 15  
 tearing 101  
 tear strength 101, 108, 123, 124, 146, 147  
 temperature 3, 4, 5, 6, 7, 9, 10, 11, 13,  
 33, 40, 41, 42, 44, 45, 47, 48, 49, 50, 52,  
 56, 57, 58, 60, 62, 63, 64, 66, 67, 74,  
 78, 81, 82, 83, 84, 86, 91, 95, 97, 98, 102,  
 109, 112, 122, 127, 131, 133, 137, 138, 141,  
 143, 144, 145, 147, 148, 154  
 – effect on viscosity 23  
 – variation 75  
 tensile strength VIII, 101, 107, 108, 109,  
 120, 122, 123, 147, 148  
 thermal stability 1  
 thermocouple 49, 50  
 thickness 48, 66, 76, 79, 81, 82, 92, 94,  
 96, 97, 101, 103, 105, 113, 114, 141, 144,  
 148, 168  
 – variation 136, 143, 145  
 throughput 14, 34, 53, 56, 58, 60, 69,  
 72, 83, 134, 137, 138, 139, 142, 161, 164,  
 165, 166  
 thrust bearing 35, 36, 37  
 tie layer 117  
 torque 4, 5, 35, 44, 53, 75

toughness 4, 11, 107, 117  
transparency 128, 146, 149  
transverse direction 83  
treatment 94  
troubleshooting 47, 52, 58, 132, 135, 150

## V

variation 69, 70, 73, 79, 91, 92, 94, 95,  
98, 131, 141  
vent 43, 64, 65  
viscosity 3, 7, 12, 14, 22, 35, 45, 51, 53,  
58, 61, 62, 65, 67, 75, 95, 111, 116, 131,  
132, 141, 154  
viscous behavior 20

## W

wear 12, 15, 41, 45, 138, 140  
weld line 76, 146  
winder 92  
winding 8, 17, 150  
wood flour 16  
wrinkle 91, 150